



Effects of SiC Wt% Content on Microstructure and Mechanical Properties of Al/SiC Nano composite Produced by Mechanical Alloying, Sintering and Milling

Najmeddin Arab

Department of Material Science Research Center, Saveh Branch, Islamic Azad University, Saveh, Iran,

*Received 06 Nov 2020,
Revised 24 Dec 2020,
Accepted 30 Dec 2020*

Keywords

- ✓ *Al/nano SiC,*
- ✓ *Mechanical Alloying,*
- ✓ *Powder Metallurgy,*
- ✓ *Mechanical Properties*
- ✓ *Microstructure*

*najmarab@iau-saveh.ac.ir ;
Phone: +988642433342;
Fax: +9886424330088*

Abstract

Nano Silicon carbide reinforced aluminum (Al/nanoSiC) metal matrix composites are attractive because of their superior properties such as high strength and stiffness, Application of aluminum in technological and structural application is growing steadily. The major limitation for metal matrix nano composites, however, is their propensity to brittle fracture. The new technologies and new materials are two basic aims for companies. In this research, the effect of addition Al/SiC nano particles on microstructure and mechanical properties of pure aluminum has been investigated. Pure aluminum powder and various fractions of SiC particles with an average diameter of 50 nm were milled by a high-energy planetary ball mill to produce nanocrystalline Al-SiC nanocomposite powders. Pressing and sintering applied to consolidate powders to tablet shape. Then the samples were rolled to cylindrical shape. The nano SiC Percentage were 0%, 2.5%, 5%, 7.5%, 10%, 12.5% and 15%. Mechanical tests such as tensile, hardness, fracture toughness and young's modules measurement carried out to study the mechanical behavior of each alloy. Scanning electron microscopy was used to study the morphology and microstructure of nanocomposite powders and bulk samples. The role of wt% fraction of SiC nanoparticles was investigated. The results shows that the addition of SiC nano particles has significant influence on the microstructure and mechanical properties of composites and usually the optimum properties depends on wt% SiC.

1. Introduction

Metal matrix composites (MMCs) are engineering materials which contain a hard ceramic particles or fibers in metallic matrix to obtain specific properties which make them superior to conventional metals and alloys. Aluminum matrix composites are important categories in these fields. It consist of a non-metallic reinforcement (SiC, B4C, Si3N4, AlN, TiC, TiB2, TiO2) incorporated into aluminum matrix which provides advantageous properties over base metal (Al) alloys. These include improved abrasion resistance, creep resistance, dimensional stability, exceptionally good stiffness-to-weight and strength-to-weight ratios and better high temperature performance, and have extended application in aerospace, automotive and high duty structures, biotechnology, electronic and sporting goods industries. The type, size and uniform distribution of the reinforcing particles in metal matrix, have critical effects on physical and mechanical properties of the composite [1- 7], Al/SiC nano composites are important group of aluminum MMCs which have higher mechanical and physical properties [8-18]. There are many researches and published papers about Al/nano SiC composites. These researches can be categorized

into 6 major fields. The studies of the first focused on manufacturing methods. The results consist of different techniques for fabrication of Al/SiC composites. The major methods of fabrications are squeeze casting, metal spray, metal infiltration, laser deposition technology and mechanical alloying, powder metallurgy, and so [19–27]. Among them, mechanical alloying have more advantages [25], although there are a lot of problems about uniform distribution of the reinforcement particles in the metal matrix. The second field, concern the role of SiC particles on formability of aluminum matrix. The results showed that nano SiC particles play like a barrier against aluminum formability [28]. The third field of researches concern corrosion behavior of Al/SiC composites [19–32]. They demonstrated that the weight loss of the composites in corrosive media depends strongly on both volume fraction and particle size of nano SiC [26–32]. The studies of 4th group focused on the role of SiC size and distribution on mechanical properties and machinability of Al/SiC nano composites [33, 34]. The 5th group researches concern mechanical, optical, thermal, and electrical properties of Al/SiC composite [35–38]. The searching results shows variation of physical and mechanical properties by variation in volume fraction and particle size of SiC Particles. The latest group investigated dimensional stability and coefficient thermal expansion (CTE) by variation in size and distribution of SiC nano particles. The CTE values of Al/nano SiC composites are important in electronic industry as electronic chips [39–40]. Particle reinforced metal matrix composites have already found commercial use on account of the fact that conventional processing techniques, such as powder metallurgy, vacuum hot pressing, co-spray deposition process, squeeze casting, and stir casting methods can be readily adopted for the processing of such materials [41–42].

2. Methodology

Mechanical alloying (MA) is high energy ball milling process by which constituent powders repeatedly deformed, fractured and welded by grinding media to form a homogeneous alloyed microstructure or uniformly dispersed particulates in a matrix [42]. The main objectives of the milling process are to reduce the particle sizes (breaking down the material), mixing, blending and particle shaping. The major process in MA for producing quality powders of alloys and compounds with well-controlled microstructure and morphology is the repeated welding, fracture, and re-welding of the reactant mixed powders. It is critical to establish a balance between fracturing and cold welding in order to mechanically alloy successfully [43].

Planetary ball milling is carried out for fabrication of engineering materials via a mechanical alloying process. In planetary ball milling, the milling media contains considerably high energy, as the milling stock and balls come off the inner wall of the vial (milling bowl) and the effective centrifugal force can reach up to twenty times of gravitational acceleration. The centrifugal forces caused by the rotation of the supporting disc and autonomous turning of the vial act on the milling charge (balls and powders). Since the turning directions of the supporting disc and the vial are opposite, the centrifugal forces alternately are synchronized and opposite. Therefore, the milling media and the charged powders alternatively roll on the inner wall of the vial, and are lifted and thrown off across the bowl at high speed. One advantage of this type of mill is the ease of handling the vials inside a glove box. The aluminum powder used in this research has a purity of 99%. The particle size of 90% of powder is about 54 nm. In this study stearic acid ($C_{18}H_{36}O_2$ or $CH_3(CH_2)_{16}COOH$) and methanol (CH_3OH) with purity of 99.99% are used as process control agent to avoid cold welding. First Suitable amount of pure powder aluminum with 5% wt% of SiC with 99% purity and particle size of 90% of powder about 76 nanometer was ball milled mixing planetary ball mill. The Transmission Electron Microscopy (TEM) of Al and SiC powders are illustrate in Figure 1.

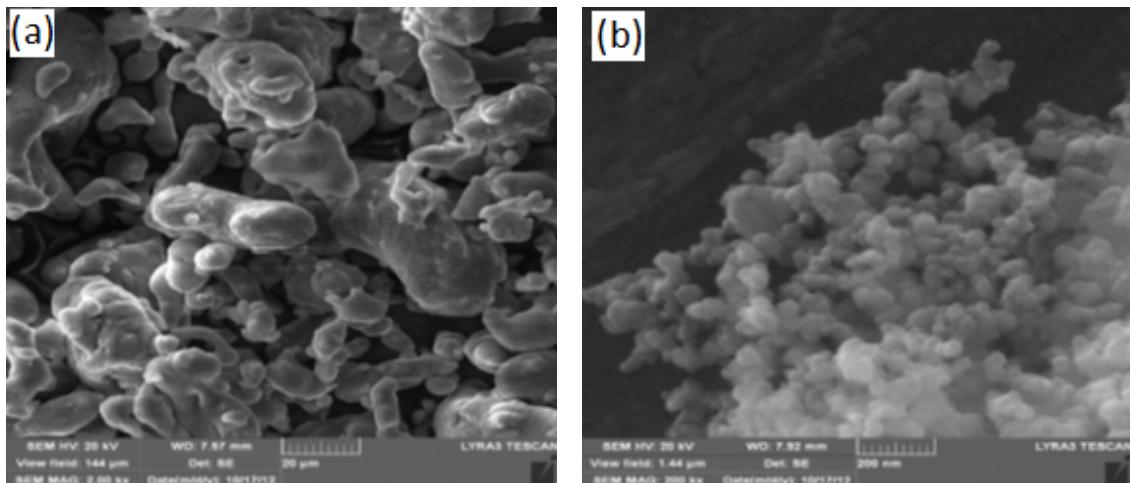


Figure 1: SEM micrograph from Nano- Powders **(a)** Pure Al , **(b)** Sic

For mixing the powder, a mixer device with effective sun wheel diameter of 300mm, speed ratio of 1:2.5, interval operation with direction reversal and 1 min pause time after each 15 min running time. The jars were ran under argon gas and then were agitated with 3 different stainless steel milling balls size of 10, 15 and 20 mm at rotation speeds of 200 rpm. The ball numbers of 100 were used for milling times 20 hr. Stearic acid [$\text{CH}_3(\text{CH}_2)_{16}\text{COOH}$] of 2 wt% and 5 ml methanol [CH_3OH] were added as a process control agent separately and giving a ball to powder weight (B/P) ratio of 10:1 to reach a fine powder particle size regarding to powder morphology and to minimize cold welding of the aluminum particles and to prevent powders from sticking to the balls and the jar wall. Mixing was carefully controlled under blowing argon inert gas with 5 liter per minute and afterward was transferred to the glove box to avoid impurities. Impurities in the sample influence the physical, interface reaction and mechanical properties of milled aluminum. For pressing of prepared powders, the mold illustrate in [Figure 2-a](#), which made from heat treated tool steel type SPK, and pressing machine in [Figure 2-b](#) with loading force 120 tons was used. The samples are shown in [Figure 3](#). The sintering operation was carried out in 0.05 bar vacuum furnace at 495°C.

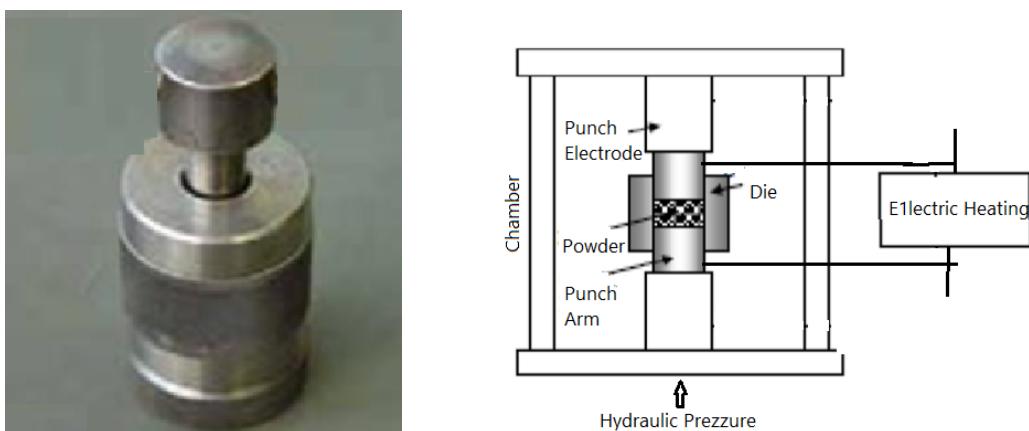


Figure 2: The mold **(a)** and tools **(b)** used in powder pressing

Then the rolling of sintered samples was carried out by a laboratory two mill with 6 Tons load capacity and 25/130 mm diameter/length mills and 20-30 RPM speed. The wire cut machine used for preparation of tensile test specimens according to ASTM A370. Then the mechanical test was carried out on specimens.

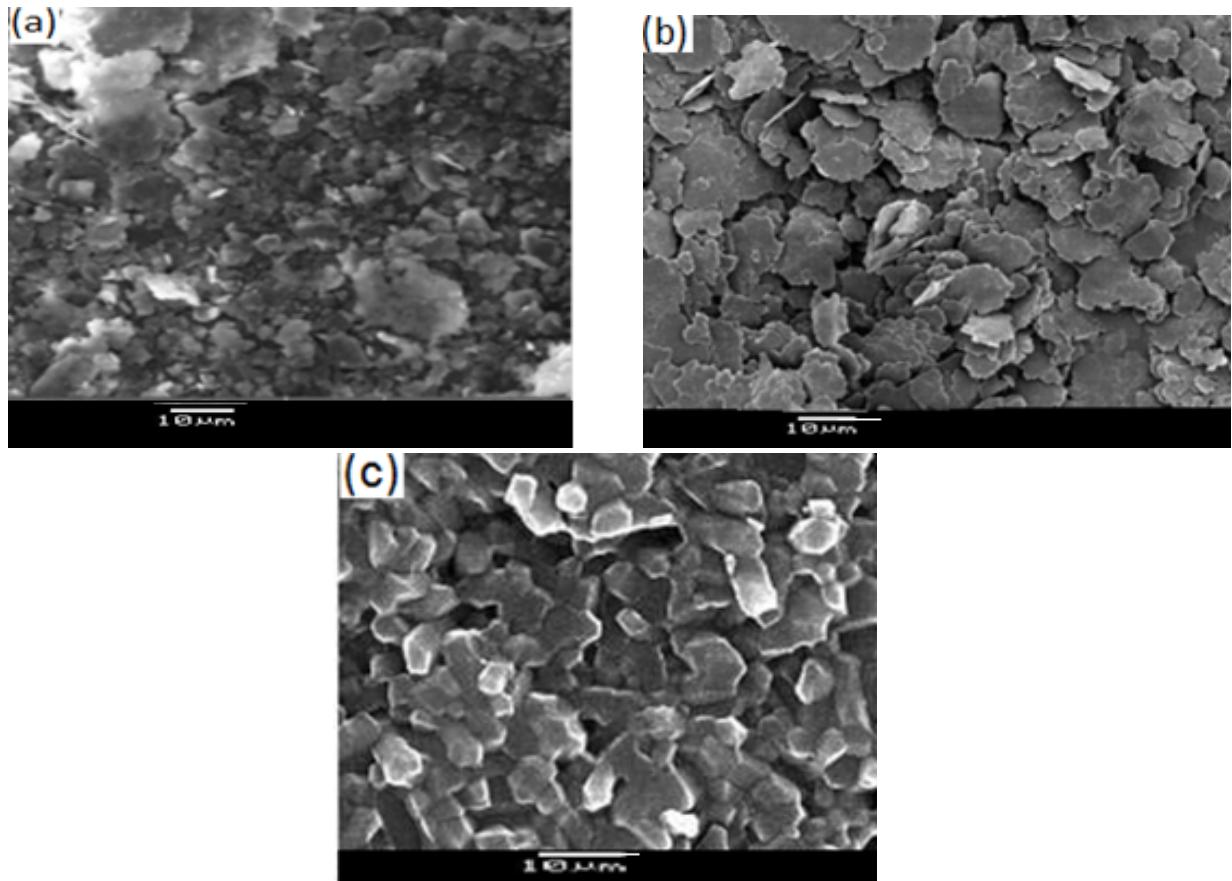


Figure 3: SEM image of : **a)** Al/SiC wt 5% with average grain size 35,9 nm , **b)** Al/SiC wt7.5% with average grain size 39.8 nm **c)** Al/SiC wt 10% with average grain size 46,2 nm , after 20 hours milling.

3. Results and Discussion

3.1. Morphology of milled powder

The Scanning Electron Microscopy ((SEM) images of mixed Al/SiC wt 5% , Al/SiC wt7.5% and Al/SiC wt 10% after 20 hours milling is illustrate in figure 3a, 3b, 3c respectively. **Figure 4** illustrated the XRD spectra of the as-received aluminum and Al-nano SiC composite powders mechanically milled for 20 hour.

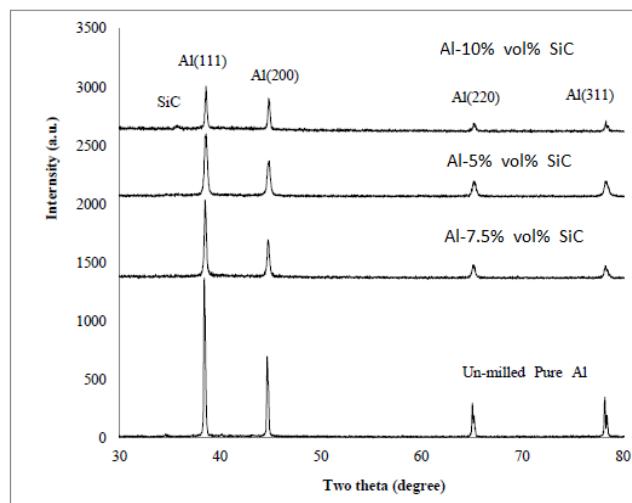


Figure 4: XRD spectra of the as-received aluminum and Al-SiC nanocomposite powder mechanically milled for 20 h.

Figure 5 shows the SEM images of rolled Al/SiC 5 and Al/SiC 7.5 wt%. It shows the powder size is effectively reduced after milling and rolling, to average 35.9 nm and 38.7 nm with good uniformity. The particle size was reduced due to high impact forces and temperature inside the jar and rolling load that forced particle towards higher density, lower porosity and closer to a spherical shape. During the milling process the temperature is going up so after a certain temperature will control the cold welding and it seems that warm welding occurred. At this stage, the impact energy is enough to break down the particles. Generally, the particle size and shape were considered as the most important factors which effect aluminum matrix and mechanical properties of samples.

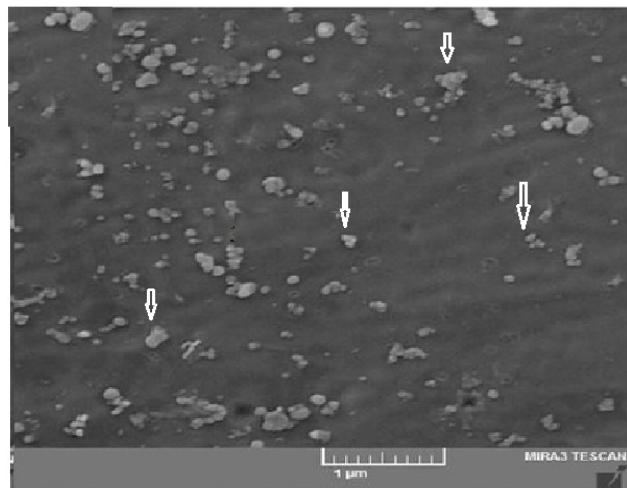


Figure 5a: SEM image of rolled nano Al/SiC 5wt%

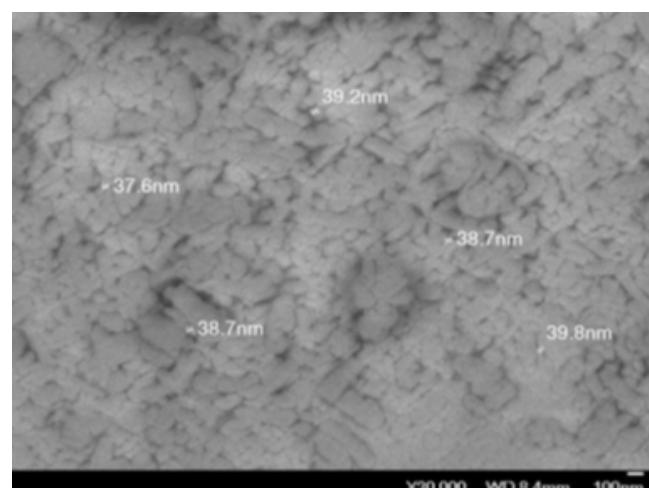


Figure 5b: SEM image of rolled nano Al/SiC 7.5 wt%.

3.2. Tensile Test

Table 1 shows the results of tensile test on specimens and **Figure 6** show engineering stress-strain curves. It shows, increasing nano SiC percentage, increase engineering tensile strength, but decrease engineering strain. SiC nano particles have roles as barriers to prevent movement of dislocations, so the required stress for dislocations movement will increase, but regarding these barriers, the engineering strain will decrease. **Figure 7** illustrate the variation of true yield and tensile strength and strain and elongation with various nano Al/SiC wt%. As nano particles increase, the ultimate tensile strength (UTS) and yield strength (YS) increase and elongation percentage decrease. The same reason about dislocation displacement is reliable for this behavior.

Table 1: Results of true tensile tests of various Al/ nano SiC wt%.

Alloy	Yield Strength (MPa)	Tensile Strength (MPa)	EI%
Pure Aluminum	54.3	85.4	27.8
Al- 2.5% SiC	118.1	132.2	11.95
Al-5% SiC	125.5	151.9	10.5
Al-7.5% SiC	133.1	159.4	9.55
Al-10% SiC	139.6	168.7	8.6
Al-12/5% SiC	149.1	177.8	7.95
Al-15% SiC	157.5	187.5	7.3

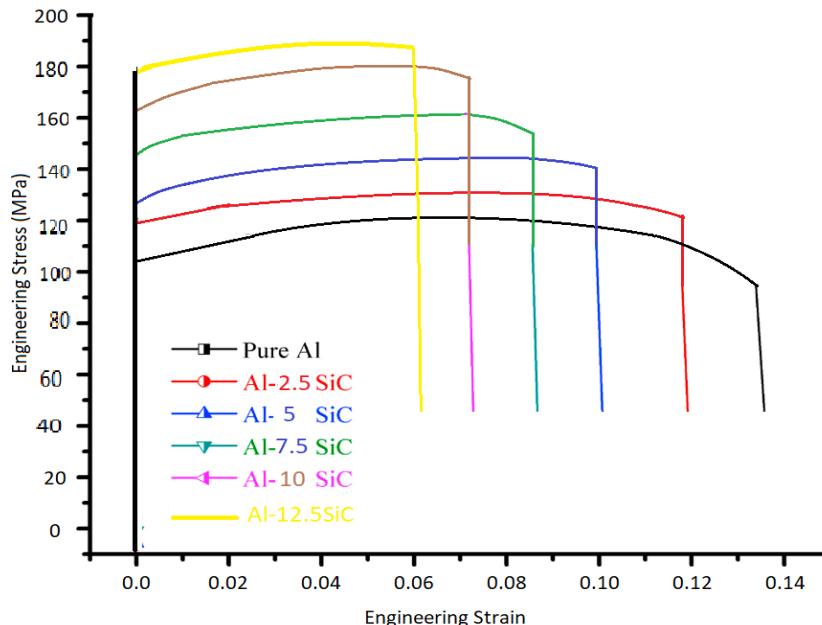


Figure 6: Engineering Stress - Strain curves for various Al/ nano SiC wt%.

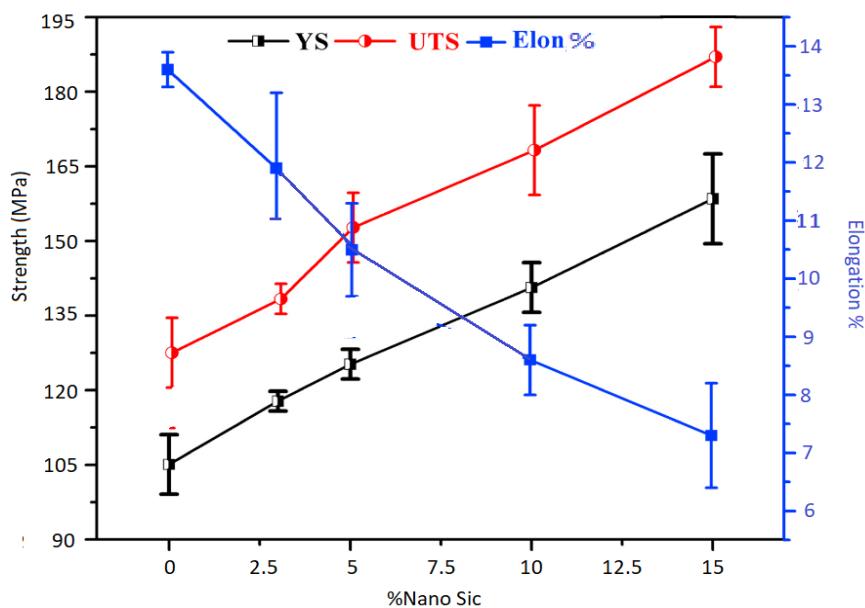


Figure 7: Yield Stress, Ultimate Tensile Strength and Elongation percentage for various versus wt% nano SiC.

Figure 8 show Young's modulus variations versus wt% nano SiC. From 0% to 2.5%, there is no visible change in results but from 2.5% to 15 wt% nano SiC, there are notable increase in young modules so it increase from 77 to 106 GPa. Reinforcement particles which are smaller than the matrix particles situate themselves between the matrix particles and fill the pores. This caused an increase in the density of the composites when compared with the Al matrix. This behavior is as a result of high mechanical properties of SiC which include relatively high yield strength, high Young's modulus, etc except its ductility that is very poor. It is then expected that these features will contribute positively on the mechanical properties of Al/SiC composites when SiC particles are uniformly dispersed as a reinforcement material. However, there is an actual SiC particles percentage addition, through which the maximum values of these mechanical properties decrease. To find this value, it is necessary to do more tests with higher nano particles addition. Beyond this value, SiC clusters form in the composites and these clusters deteriorate the mechanical properties of the composites by lowering its values.

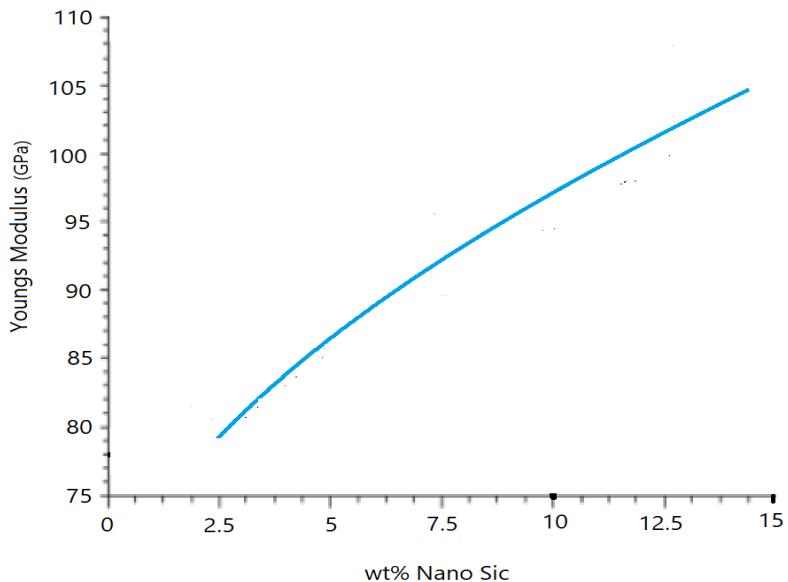


Figure 8: Young's modulus variations versus wt% nano SiC.

3.3. Hardness Test

Table 2 and **Figure 9** show hardness variation versus wt% nano SiC. Silicon carbide particles are hard phase and distribution of these particles in aluminum matrix, increase hardness of alloy. Higher wt% nano SiC, increase hardness of matrix, so the hardness increases by 32% when wt% nano SiC increase from 2.5% to 15%.

Table 2: Brinell hardness of samples

Alloy	Aluminum	Al- 2.5% SiC	Al-5% SiC	Al-7.5% SiC	Al-10% SiC	Al-12/5% SiC	Al-15% SiC
Brinell Hardness	23	79	86	92	96.8	101.3	106

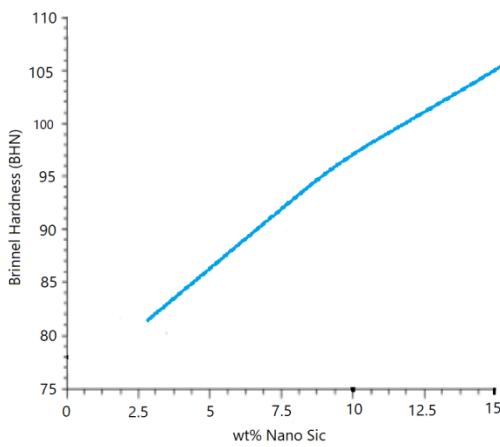



Figure 9: Hardness variations versus wt% nano SiC.

3.4. Fracture Toughness Test

Six blanks of 12.7 x 63.5 x 63.5 mm were cut from the raw samples where the blanks were further machined to final dimensions of the Compact Specimens as specified in ASTM Standard E399-83". The specimens were 12.7 mm thick and notched in the L-T orientation according. **Table 3** and **Figure 10** shows fracture toughness test results for various Al wt% nano SiC. The Fracture Toughness increase from 48 in 2.5wt% nano Si to 55 MPa.m^{0.5} at 10%.

Table 3: Fracture Toughness test Results

Alloy	Aluminum	Al- 2.5% SiC	Al-5% SiC	Al-7.5% SiC	Al-10% SiC	Al-12/5% SiC	Al-15% SiC
Fracture Toughness MPa.m ^{0.5}	35.6	48	52	56	55	50	49

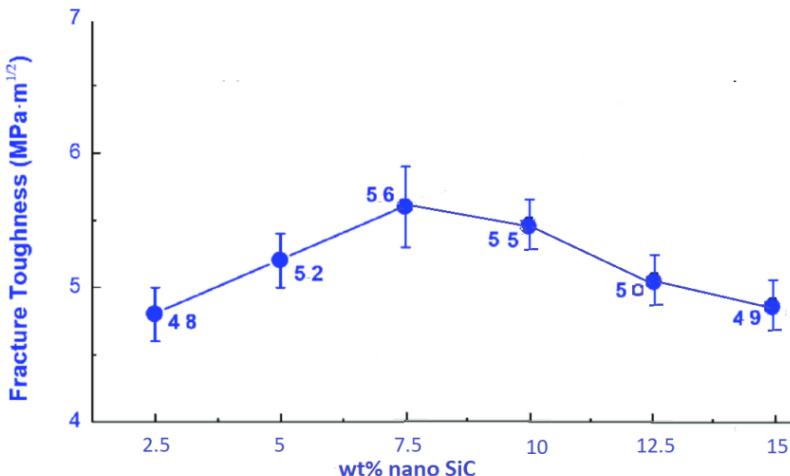**Figure 10:** Fracture toughness variation versus wt% nano SiC.

As can be see, that fracture toughness increased significantly by addition of wt% nano SiC reinforcement particles up to 7.5%, but in higher amount decrease. It can be describe by increasing the stress concentration sites by increasing particles amount. At 2.5-7.5% wt% nano SiC, There is 2 different behaviors. First one increasing the mechanical properties and second the stress concentration sites which decrease toughness behavior. But the mechanical properties have higher influence on fracture toughness than sites, and the total fracture toughness increase. When wt% nano SiC increased more than 7.5%, the stress concentration sites have higher influence and reduce final fracture toughness.

Conclusion

The reinforcement of Al alloys with nano SiC particulates has led to the development of a group of composite materials with very interesting properties. This research considered aluminum metal matrix reinforced by nano silicon carbide particles by mechanical alloying process. In particular, Al/nano SiC composites exhibit better stiffness and strength than the corresponding unreinforced alloys. The main limitation of Al/SiC nano composites to be used as structural elements arises from their reduced ductility and fracture toughness specially at high amount of nano SiC induced by the presence of brittle, ceramic reinforcements, so the study of the fracture behavior has received increasing attention from the research community in recent years.

The prepared samples provide higher mechanical properties than the commercial composite materials. Mechanical tests show increase in reinforcement particles can increase the yield and tensile strength, hardness, and also modify the fracture toughness at certain percentage of wt% nano SiC. Fracture toughness increased significantly by addition up to 7.5%. Higher contents, reduced the fracture toughness of the composites. This was mainly attributed to premature yielding caused by the high ductility/low strength of the Al matrix.

References

- [1] D. B. Miracle, "Metal matrix composites from science to technological significance" *Composites Science and Technology*, 65 (2005) 2526–2540.
- [2] A. Bhaduri, V. Gopinathan, P. Ramakrishnan, and A. P. Miodownik, "Processing and properties of SiC particulate reinforced Al-6.2Zn-2.5Mg-1.7Cu alloy (7010) matrix composites prepared by mechanical alloying", *Materials Science and Engineering A*, 221 (1996) 94-101.
- [3] L M. Tham, M. Gupta, L. Cheng, "Effect of limited matrix-reinforcement interfacial reaction on enhancing the mechanical properties of aluminum-silicon carbide composites", *Acta mater*, 49 (2001) 3243–3253.
- [4] Y. Yang, J. Lan, X. Li, "Study on bulk aluminum matrix nano-composite fabricated by ultrasonic dispersion of nano-sized SiC particles in molten aluminum alloy", *Materials Science and Engineering A*, 380 (2004) 378-383.
- [5] A. S. Babu, V. Jayabalani, "Weibull Probability Model for Fracture Strength of Aluminum (1101)-Alumina Particle Reinforced Metal Matrix Composite", *J. Mater. Sci. Technol.* 25 (2009) 341-343.
- [6] T. Rostamzadeh, H. R. Shahverdi, R. Mamoory, "Investigation the effect of volume fraction reinforcement phase on Microstructure of Al-SiC nanocomposite powder prepared via mechanical alloying", *Advanced Materials Research*, 83 (2010) 764-770.
- [7] B. Prabhu, C. Suryanarayana, L. An, R. Vaidyanathan, "Effect of Reinforcement Volume Fraction on the Mechanical Properties of Al—SiC Nano composites Produced by Mechanical Alloying and Consolidation", *Material Science and Engineering*, 425 (2006) 192-200.
- [8] S. F. Hassan, M. Gupta, "Effect of Type of Primary Processing on the Microstructure, CTE and Mechanical Properties of Magnesium/Alumina Nano composites", *Composite Structures*, 72 (2006) 19–26.
- [9] K. B. Lee, H. S. Sim, "Fabrication and characteristics of AA6061/SiC composites by pressureless infiltration technique", *Journal of Material Science*, 36 (2001) 3179 – 3188.
- [10] B. Ogel, and R. Gurbuz, "Microstructural Characterization and Tensile Properties of Hot Pressed Al-Sic Composites Prepared From Pure Al and Cu Powders", *Materials Science and Engineering A*, 301 (2001) 213-220.
- [11] Y. Ozcatalbas, "Investigation of the machinability behaviour of Al₄C₃ reinforced Al-based composite produced by mechanical alloying technique", *Compos. Sci. Technol.* 63 (2008) 53-61.
- [12] A. Simchi, S. Kamrani, S.M. Seyed Reihani, "Processing of Al/SiC nanocomposite powder by high energy ball milling" *Journal of Materials processing Technology*, 186 (2007) 283-294.
- [13] J. M Wu, Z. Z. Li, "Nanostructured composite obtained by mechanically driven reduction reaction of CuO and Al powder mixture", *Journal of Alloys and Compounds*, 299 (2000) 9–16.
- [14] Z. Razavi Hesabi, A. Simchi, SM. Seyed Reihani, "Structural Evolution during Mechanical Milling of Nanometric and Micrometric Al₂O₃ Reinforced Al Matrix Composite" *Material Science Engineering A*, 428 (2006) 159-168.
- [15] D. B. Witkin, E. J. Lavernia, "Synthesis and mechanical behavior of nanostructured materials via cryomilling", *Progress in Materials Science*, (2006) 51 1–60.
- [16] D. L. Zhang, "Processing of Advanced Materials Using High-Energy. Mechanical Milling", *Progress in Materials Science*, 49 (2004) 537–560.
- [17] S. Deb, S. K. Panigrahi, "Development of bulk ultrafine grained Al-SiC nano composite sheets by a SPD based hybrid process: Experimental and theoretical studies", *Materials Science and Engineering. A, Structural Materials: Properties, Microstructure and Processing*, 738 (2017) 323-334.

- [18] S. M. Shirazi, F. Akhlaghi, "Tribological behavior of Al/SiC and Al/SiC/2 vol%Gr nanocomposites containing different amounts of nano SiC particles", *Materials Research Express*, 6 (2019) 18-17.
- [19] O. Gingi, M. Mangra, and R. L. Orban, "In-situ production of Al/SiCp composite by laser deposition technology," *Journal of Materials Processing Technology*, 90 (1999) 187–190.
- [20] Y. Sahin and G. Sur, "The effect of Al₂O₃, TiN and Ti (C,N) based CVD coatings on tool wear in machining metal matrix composites," *Surface and Coatings Technology*, 79 3 (2004) 349–355.
- [21] J. Rodriguez, M. A. Garrido-Maneiro, P. Poza, and M. T. Gomez del Rio, "Determination of mechanical properties of aluminium matrix composites constituents," *Materials Science and Engineering A*, 437 2 (2006) 406–412.
- [22] D. P. Mondal, N. V. Ganesh, V. S. Muneshwar, S. Das, and N. Ramakrishnan, "Effect of SiC concentration and strain rate on the compressive deformation behavior of 2014Al-SiCp composite," *Materials Science and Engineering A*, 433(2) (2006) 18–31.
- [23] J. Hashim, L. Looney, and M. S. J. Hashmi, "Metal matrix composites: production by the stir casting method," *Journal of Materials Processing Technology*, 93 (1999) 1–7.
- [24] J. Hashim, L. Looney, and M. S. J. Hashmi, "Particle distribution in cast metal matrix composites- Part II," *Journal of Materials Processing Technology*, 123 (2002) 258–263.
- [25] S. Naher, D. Brabazon, and L. Looney, "Simulation of the stir casting process," *Journal of Materials Processing Technology*, 144(1) (2003) 567–571.
- [26] P. K. Ghosh and S. Ray, "Fabrication and properties of compocast aluminum-alumina particulate composite," *Indian Journal of Technology*, 26(2) (1988) 83–94.
- [27] J.B. Fogagnolo, E.M. Ruiz-Navas, M. H. Robert, and J.M. Torralba, "The effects of mechanical alloying on the compressibility of aluminum matrix composite powder", *Materials Science and Engineering A*, 355 2 (2003) 50–55.
- [28] S. Candan, "Effect of SiC particle size on corrosion behavior of pressure infiltrated Al matrix composites in a NaCl solution" *Materials Letters*, 58(28) (2004) 3601–3605.
- [29] S. Vijayabhaskar, T. Rajmohan, T.K. Vignesh, H. Venkatakrishnan, "Effect of nano SiC particles on properties and characterization of Magnesium matrix nano composites," *Materials Today, Proceedings*, 16(2) (2019) 853-858.
- [30] A. A. Premnath, P. L. Varma, P. S. Rama Krishna, P. Dheeraj, and P. Karthik, "Mechanical properties of Al-SiC Nano Composites fabricated by Friction Stir Processing" The 3rd International Conference on Materials and Manufacturing Engineering, (2018).
- [31] K. Gopinath, R. Balasubramaniam, and V. S. R. Murthy, "Corrosion behavior of cast Al-Al₂O₃ particulate composites", *Journal of Materials Science Letters*, 20 9 (2001) 793–794.
- [32] R. C. Paciej and V. S. Agarwala, "Influence of processing variables on the corrosion susceptibility of metal-matrix composites", *Corrosion*, 44(10) (1988) 680–684.
- [33] C. Kaynak and S. Boylu, "Effects of SiC Particulates on the Fatigue Behavior of an Al-Alloy Matrix Composite," *Materials & Design*, 27 (2006) 776–782.
- [34] X. Zeng, W. Liu, B. Xu, G. Shu and Q. Li, "Microstructure and Mechanical Properties of Al–SiC Nanocomposites Synthesized by Surface-Modified Aluminum Powder", *Metals*, 8(4) (2018) 253–259.
- [35] N. Chawla, J. J. Williams, and R. Saha, "Mechanical behavior and microstructure characterization of sinter-forged SiC particle reinforced aluminum matrix composites," *Journal of Light Metals*, 2(4) (2002) 215–227.
- [36]. Z. Gnjidi, C. D. Bozic, and M. Mitkov, "The influence of SiC particles on the compressive properties of metal matrix composites", *Materials Characterization*, 47(2) (2001) 129–138.

- [37] A. Martin, M. A. Martinez, and J. Lorca, “Wear of SiC reinforced Al-matrix composites in the temperature range 20–200°C,” *Wear*, 193 (2006) 169–179.
- [38] E. Candan, “Effect of alloying additions on the porosity of SiCp preforms infiltrated by aluminum”, *Materials Letters*, 60(10) (2006) 1204–1208.
- [39] V. P. Klyuev and B. Z. Pevzner, “The influence of aluminum oxide on the thermal expansion, glass transition temperature and viscosity of lithium and sodium aluminoborate glasses”, *Glass Physics and Chemistry*, 28 4 (2002) 207–220.
- [40] S. M. Zebarjad, S. A. Sajjadi, and E. Z. Vahid Karimi, “Influence of Nanosized Silicon Carbide on Dimensional Stability of Al/SiC Nanocomposite”, *Research Letters in Materials Science*, (2008), Article ID 835746, 4 pages, doi:10.1155/2008/835746.
- [41] BF. Luan, N. Hansen, A. Godfrey, G.H. Wu, Q. Liu “High strength Al-Al₂O₃p composites: Optimization of extrusion parameters”, *Materials Design*, 32 (2011) 3810–3817.
- [42] C. Suryanarayana, “Mechanical alloying and milling progress”, *Materials Science*, 46 (2001) 1–184.
- [43] M. Ramezani, T. Neitzert, “Mechanical milling of aluminum powder using planetary ball milling process” *Journal of Achievements in Materials and Manufacturing Engineering*, 55(2) (2012) 790-798.

(2020) <http://www.jmaterenvironsci.com>